



## **UWL REPOSITORY**

**[repository.uwl.ac.uk](https://repository.uwl.ac.uk)**

Shear behavior of high strength fiber reinforced concrete beams under different levels of axial compression forces

Shaaban, Ibrahim ORCID: <https://orcid.org/0000-0003-4051-341X> (2006) Shear behavior of high strength fiber reinforced concrete beams under different levels of axial compression forces. In: 10th Arab Structural Engineering Conference, 13-15 Nov. 2006, Kuwait.

**This is the Draft Version of the final output.**

**UWL repository link:** <https://repository.uwl.ac.uk/id/eprint/6975/>

**Alternative formats:** If you require this document in an alternative format, please contact: [open.research@uwl.ac.uk](mailto:open.research@uwl.ac.uk)

### **Copyright:**

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy:** If you believe that this document breaches copyright, please contact us at [open.research@uwl.ac.uk](mailto:open.research@uwl.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.

## **SHEAR BEHAVIOR OF HIGH STRENGTH FIBER REINFORCED CONCRETE BEAMS UNDER DIFFERENT LEVELS OF AXIAL COMPRESSION FORCES**

IBRAHIM G. SHAABAN

*Department of Civil Engineering, Banha University  
Faculty of Engineering, 108 Shoubra St. Cairo, Egypt*

**ABSTRACT:** This study is part of a larger research work aimed to study the effects of fiber content, fiber type (corrugated shape and hooked-end), amount of web reinforcement and axial compression stress, on the shear behavior of high strength fiber reinforced concrete (HSFRC) beams. To the author's knowledge, the effect of applying axial compression forces, to the HSFRC beams, has not yet been studied. Nineteen simply supported HSFRC beams were subjected to axial compression forces and tested under two-point vertical loading for three values of shear span to depth ratio. It was found that the shear strength of beams subjected to axial compression stress level equals 0.1, is higher than that in the literature for beams tested without applying axial stress by a range of 22% -98%. Increasing the axial compression stress level to 0.2 led to an increase in the first crack load, ultimate load by 24% and 10%, a reduction in the deflection by (19-30%), compared with those subjected to axial compression stress level equals 0.1. In addition, a combination of web reinforcement and fibers resulted in a significant increase in the cracking and ultimate loads by 123 and 59%, respectively, over those of the reference beam. A new formula is proposed for predicting the experimental shear strength of HSFRC beams subjected to axial compression forces. The results obtained by the proposed formula are in better agreement with the test results when compared with the predictions based on the empirical equations proposed by other investigators.

### **INTRODUCTION**

High Strength Concrete (HSC) is considered to be a relatively brittle material because the post-peak portion of its stress-strain diagram descends deeply as compressive strength increases<sup>1, 2</sup>. When added to concrete mixes, steel fibers distribute randomly through the mix at much closer spacings than conventional reinforcing steel and act to arrest cracking by decreasing the stress intensity factor at the tip of inherent internal cracks<sup>3</sup>. This leads to increasing the shear-friction strength of concrete and also improves the ultimate tensile strength and ductility because a lot of energy is absorbed in debonding and pulling out of fibers from the concrete before complete separation and failure of concrete occurs<sup>3</sup>. Swamy and Bahia<sup>4</sup> showed that fibers act as effective shear reinforcement, much like the legs of regularly spaced stirrups, and are more effective in arresting crack propagation and maintaining the integrity of the surrounding concrete. Craig<sup>5</sup> showed that it is possible to replace stirrups partially or completely with fibers in beams of HSC under transverse loading to resist shear. The ACI Committee 544<sup>6</sup> defined the FRC as a concrete with increased strain capacity, impact resistance, energy absorption, and tensile strength. It has been clearly shown that for beams reinforced with a fixed amount of minimum shear reinforcement, irrespective of the concrete strength, the reserve shear strength diminishes as the concrete strength gets higher<sup>7, 8</sup>. Therefore, the minimum shear reinforcement for HSC either in the form of stirrups, fibers or both needs more investigation.

Despite that the behaviour of reinforced concrete (RC) beams in flexure and shear was examined in the literature using an independent test specimen without restraints, RC beams in real concrete structures are members of a frame structure and they behave differently from such idealized members because of the axial restraint imposed by adjacent members<sup>9</sup>. Based on experiments and analyses, researchers<sup>10</sup> have concluded that reinforced concrete member's characteristics, such as capacity and failure pattern in compression, are significantly different under restraint conditions. Yang et al.<sup>9</sup> showed that the flexural and shear behavior characteristics and the failure pattern of RC flexural members is governed by the intensity of axial restraints. Abdoun<sup>11</sup> studied the effect of axial compression forces on the behavior of HSC beams with web reinforcement. To date, an organized and comprehensive evaluation considering the effect of applying axial compression forces to the fiber reinforced HSC beams without web reinforcement, has not been attempted.

The aim of this research is to study the effect of varying the fiber type, fiber content and the axial compression forces on the shear behavior of HSFRC beams. All studied beams were subjected to axial compression forces and then tested by two-point transverse loading. The resulting first-crack loads and ultimate shear loads were compared with those of a plain concrete reference beam to assess the contribution of the fibers. A proposed formula was developed for prediction of shear strength of studied beams to a high degree of accuracy.

## EXPERIMENTAL PROGRAMME

### *Preparation of Beam Specimens and Testing*

Mix proportions for HSC used in this study are shown in Table 1. Steel fibers of varying amounts and types (see Table 2) were added during mixing of the concrete. Two types of fibers were used, namely, hooked-end and corrugated steel fibers of yield strength of 400 MPa. The aspect ratio of the two types of fibers was constant ( $\ell/d_f = 50 \text{ mm} / 1 \text{ mm} = 50$ ). Dimensions and details of specimens used in this research are shown in Table 2 and Figure 1. It should be noted that all beams were over-reinforced in flexure to ensure shear failure. The tested beam specimens were subjected to axial compression force prior to testing by two-point transverse loading (shear span-to depth ratio,  $a/d = 2, 3$  and  $4$ ). All beams were statically tested to failure in a single load cycle. A Linear Variable Differential Transducer (LVDT) was used to measure deflection, strains at bottom bars and stirrups from the electrical strain gauges through a computer-controlled data acquisition system.

Table 1 Mix Constituent Proportions for the Studied Beams

<i>Characteristic strength</i>	<i>PROPORTIONS, kg/m<sup>3</sup></i>					
	<i>Cement</i>	<i>Sand</i>	<i>Crushed Basalt</i>	<i>Silica Fume</i>	<i>Water</i>	<i>Superplasticizer Liter/ m<sup>3</sup></i>
80 MPa	550	600	1250	55	150	23

## EXPERIMENTAL RESULTS AND DISCUSSION

### *General Behavior, Crack Pattern and Failure Mode*

Figure 2 shows the crack pattern and failure mode for all the tested beams. The first crack load, ultimate load capacity and modes of failure for the tested beams are listed in Table 3. Generally, the first crack for all beams occurred in the shear region perpendicular to the direction of the maximum principal stress induced by pure shear. Despite that the type and amount of steel fibers

did not change the mode of failure, they transformed the failure mode into a more ductile one, or in other words, they raised the value of the first crack and ultimate loads as shown in Table 3. For example, adding 0.5% fibers by volume resulted in increasing the cracking load and ultimate load for B1 by 14 and 17%, over those of the reference beam, B13. Increasing the fiber volume to 1.5% led to a further increase to cracking and ultimate loads for B3 by 41 and 48%, compared to those of the reference beam, B13. It was also observed that beams without web reinforcement had only a single diagonal crack on one end of the beam extending throughout the shear span (Beams B1-B13). In addition, Table 3 shows that the hooked-end fibers are slightly better than corrugated steel fibers in terms of raising the first crack load, increasing the capacity and ductility of studied beams. For example, Beams B1 and B2 (contains hooked-end fibers and subjected to axial compression stress level equals 0.1) had a first crack load, failure load and, in turn, ductility higher than those of Beams B9 and B10 (contains corrugated steel fibers), but the failure mode did not change. Balaguru and Shah<sup>12</sup> reported the superior properties of hooked-end fibers over the other steel fibers.

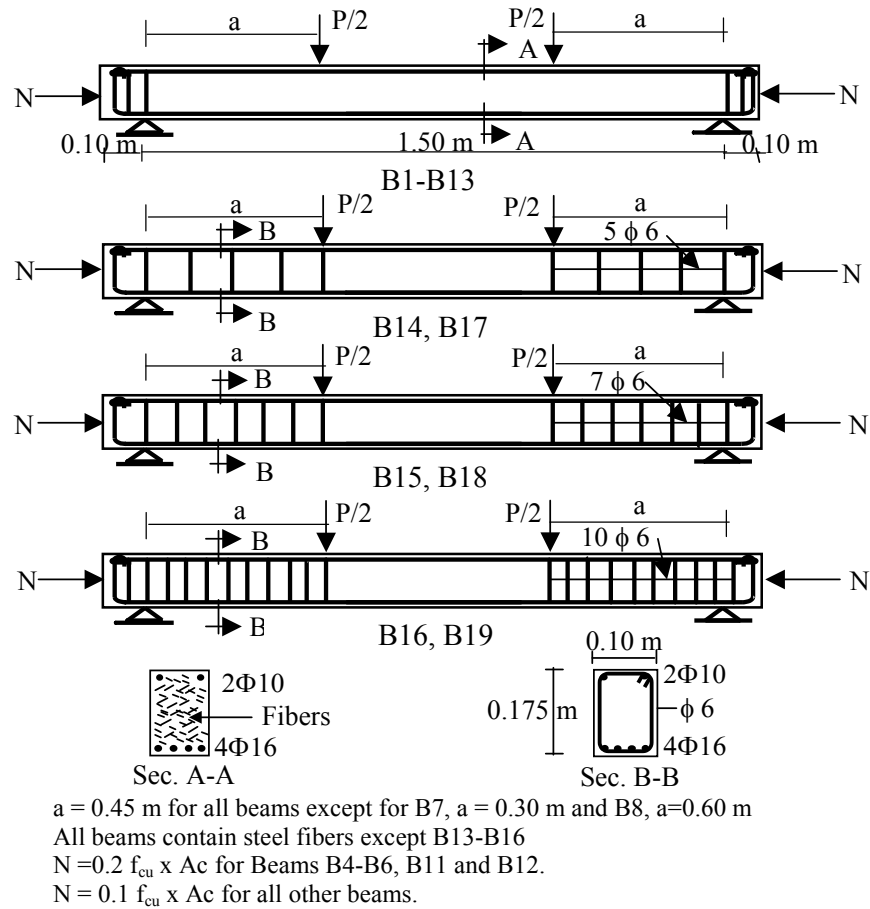


Figure 1 Dimensions, reinforcement details and loading of the studied beams.

Table 2 Experimental Programme for Studied Specimens

Beam Specimen number	$f_{cw}$ MPa	Axial compression stress ( $N/f_{cu} A_c$ )	Type of steel fibers	Volume content of fibers, $v_f$ , %	Shear span/depth ratio, $a/d$	Web reinforcement ratio, $\mu_v$ , %
B1	90	0.1	Hooked-end	0.5	3	-
B2	91	0.1	Hooked-end	1.0	3	-
B3	90	0.1	Hooked-end	1.5	3	-
B4	84	0.2	Hooked-end	0.5	3	-
B5	77	0.2	Hooked-end	1.0	3	-
B6	76	0.2	Hooked-end	1.5	3	-
B7	84	0.1	Hooked-end	1.0	2	-
B8	79	0.1	Hooked-end	1.0	4	-
B9	85	0.1	Corrugated	0.5	3	-
B10	86	0.1	Corrugated	1.0	3	-
B11	79	0.2	Corrugated	0.5	3	-
B12	80	0.2	Corrugated	1.0	3	-
B13	78	0.1	-	-	3	-
B14	78	0.1	-	-	3	0.50
B15	79	0.1	-	-	3	0.75
B16	78	0.1	-	-	3	1.12
B17	84	0.1	Hooked-end	0.5	3	0.50
B18	80	0.1	Hooked-end	0.5	3	0.75
B19	82	0.1	Hooked-end	0.5	3	1.12

It was observed that the number of inclined cracks increased with the presence of web reinforcement, indicating an enhanced redistribution of internal forces (Beams B14-B19). The combination of fibers and web reinforcement (B17-B19) resulted in a significant increase in the cracking loads (81-123%) and ultimate loads (35-59%) over those of the reference specimen B13. This is in agreement with the findings of Johnson and Ramirez<sup>7</sup>. For Beams B14, the mode of failure was shear-compression, but adding steel fibers in B17 resulted in raising the first crack load and ultimate load by 20 and 8%, respectively. Increasing the amount of transverse reinforcement in B15 resulted in propagation of flexural cracks in the beam but the mode of failure was shear. Adding fibers to the mix, B18 led to improving the shear behavior and changing of failure mode and the beam failed in flexure with crushing of concrete and yielding of compression steel in top of the beam. Further increase to the web reinforcement, B16, led to decreasing the cracks spacing, increasing the number of cracks and changing the failure mode to compression failure, since the tension zone was over reinforced. In addition, increasing the applied axial compression stress from 0.1 to 0.2 led to increasing the first crack load and ultimate load. For example, increasing the applied axial compression stress from 0.1 for B1, B2 and B3 to 0.2 for B4, B5 and B6 led to increasing the cracking loads by 24, 17 and 11% and ultimate loads by 10, 6 and 3%, for these beams, respectively. It is interesting to notice that the effect of increase in axial compression stress becomes less significant with the increase of percentage volume of fibers from 0.5% to 1.5%.

## PREDICTION OF SHEAR STRENGTH

### *Proposed Equation for Predicting Shear Strength Results*

Based on the author's experimental results, the equation developed by Oh et al.<sup>13</sup> for normal strength FRC was modified to predict the experimental results in this investigation. The details of the formulation and modifications are stated elsewhere<sup>14</sup>. The proposed equation of shear strength was written as;

$$\text{for } a_s / d \geq 2.5$$

$$V_u = [(23 \rho f_c' d / a_s)^{1/3} b d + 0.9 A_v f_y d / s + 0.41 \tau F] (1 + 0.07 N / A_c) \quad (1a)$$

and for  $a_s / d < 2.5$

$$V_u = [(660 \rho f_c')^{1/3} (d / a_s)^{4/3} b d + 0.9 A_v f_y d / s + 0.41 \tau F] (1 + 0.07 N / A_c) \quad (1b)$$

where

$a_s$  is the shear span, mm;  $b$  is the breadth of beam section, mm;  $d$  is the depth of beam section, mm;  $f_c'$  is the compressive strength of cylinder specimens, MPa;  $\rho$  = percentage of area of tensile steel to area of concrete;  $\tau$  is the average fiber matrix interfacial bond stress, = 4.15 MPa;  $A_v$  is the area of stirrups, mm<sup>2</sup>;  $s$  is the spacing of the stirrups, mm;  $f_y$  is the yield strength of the stirrups, MPa;  $F_1$  is the ultimate force sustained by the steel fibers per unit area of crack at failure;  $N$  = axial compression force applied to the beam;  $A_c = b d$  (cross sectional area of beam section).

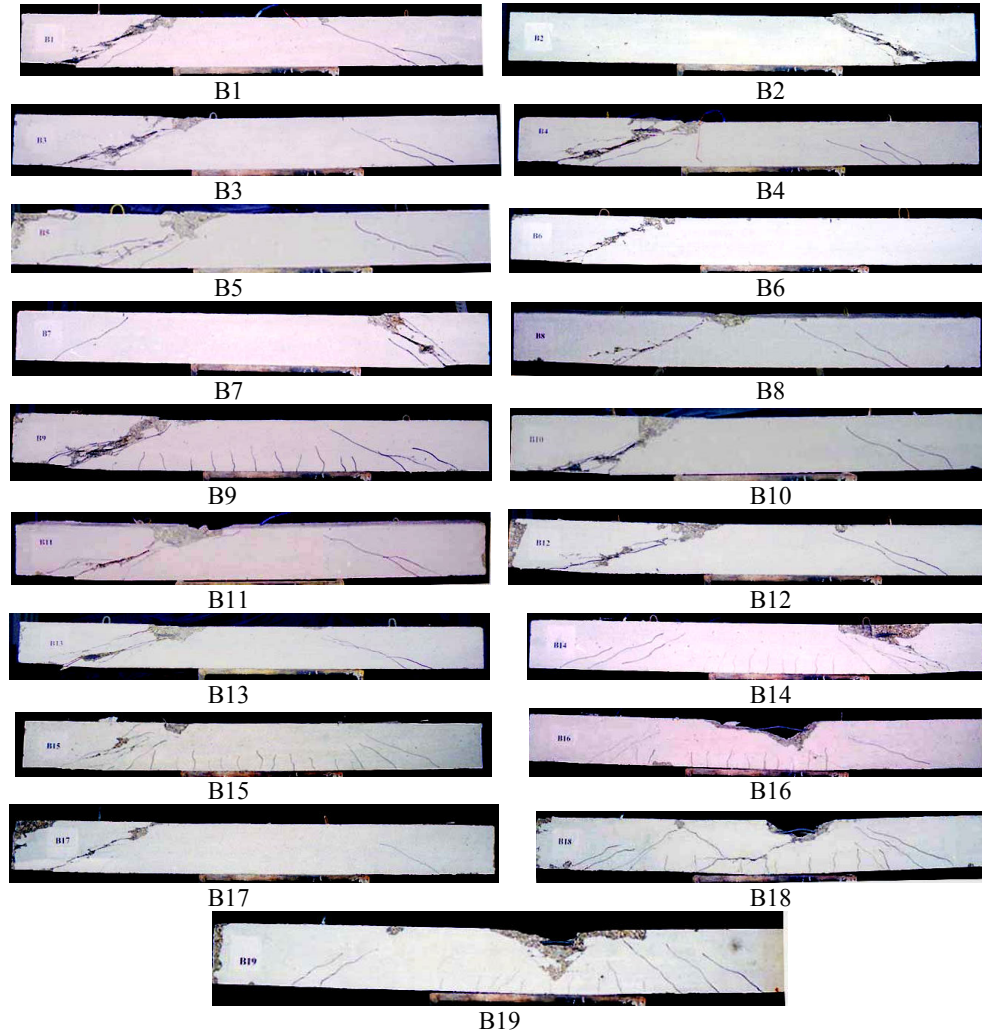


Figure 2 Crack pattern and failure mode for studied beam specimens.

Table 3 Cracking, Maximum Shear Load, and Failure Mode of the Test Beams

BEAM	$f_{cu}$ MPa	a/d	FIBER TYPE & CONTENT, $v_f$ %	ACS	$\mu_v$ , %	$P_{cr}$ , kN	$P_u$ , kN	FAILURE MODE
B1	90	3	HE, 0.5	0.1	--	121	186	Shear
B2	91	3	HE, 1.0	0.1	--	132	200	Shear
B3	90	3	HE, 1.5	0.1	--	149	236	Shear
B4	84	3	HE, 0.5	0.2	--	150	205	Shear
B5	77	3	HE, 1.0	0.2	--	155	212	Shear
B6	76	3	HE, 1.5	0.2	--	166	244	Shear
B7	84	2	HE, 1.0	0.1	--	180	288	Shear
B8	79	4	HE, 1.0	0.1	--	93	152	Shear
B9	85	3	CR, 0.5	0.1	--	117	185	Shear
B10	86	3	CR, 1.0	0.1	--	130	194	Shear
B11	79	3	CR, 0.5	0.2	--	132	197	Shear-Compression
B12	80	3	CR, 1.0	0.2	--	157	201	Shear-Compression
B13	78	3	--	0.1	--	106	159	Shear
B14*	78	3	--	0.1	0.5	160	199	Shear-Compression
B15*	79	3	--	0.1	0.75	174	234	Shear
B16*	78	3	--	0.1	1.12	210	236	Compression
B17*	84	3	HE, 0.5	0.1	0.5	192	215	Shear
B18*	80	3	HE, 0.5	0.1	0.75	227	249	Compression
B19*	82	3	HE, 0.5	0.1	1.12	236	253	Compression

ACS = axial compression stress,  $P_u$  = ultimate load,  $P_{cr}$  = cracking load, HE= hooked-end fibers, CR = corrugated steel fibers.

\* Beams with web reinforcement “stirrups”

Table 4 shows a comparison between the modified equations in the literature, which were originally proposed by Ashour et al.<sup>2</sup>, Narayanan and Darwish<sup>15</sup>, and Farahat<sup>16</sup> and the proposed equation in predicting the experimental results in this investigation. The equations in the literature were modified by multiplying their results by the factor  $(1 + 0.07 N / A_c)$  in order to include the effect of axial compression forces. This factor was included in the ACI Building Code equation<sup>17</sup> and the ECCS Code equation<sup>18</sup>. It can be seen from Table 4 that the equations developed by Ashour et al.<sup>2</sup>, Narayanan and Darwish<sup>15</sup> and Farahat<sup>16</sup> improved greatly after including the effect of axial compression forces. The ratio of the experimental to the predicted shear strength by the modified equation developed earlier by Farahat<sup>16</sup> has a mean of 1.04 and a standard deviation of 0.14, while that of the Narayanan and Darwish equation<sup>15</sup> has a mean of 1.1 with a standard deviation of 0.12 and Ashour et al. equation<sup>2</sup> predicted the results with a mean ratio of 1.18 and a standard deviation of 0.15. The proposed equation predicted the results very accurately with a mean of the experimental to the predicted results equals 1.0 and the standard deviation was 0.08 only. In order to assess the effect of axial compression forces applied to the studied beams, a comparison was made in Table 4 between the shear strength results in the current investigation and those tested by Farahat<sup>16</sup> and not subjected to axial compression forces. It can be seen that shear strength results for beams subjected to axial compression forces are higher than those tested without applying axial forces by a range of 22-98%.

## CONCLUSIONS

A total of 19 HSFRC beams, containing longitudinal reinforcement and subjected to axial compression forces, were tested. Based on the experimental results and the analytical model developed in this research, the following conclusions were drawn:

1. Test results indicated that the addition of steel fibers enhanced initial stiffness, cracking loads, ultimate loads and, shear strength, and in turn, the ductility of the studied beams. Adding

0.5% fibers by volume resulted in increasing the cracking load and ultimate load by 14 and 17% over those of the reference beam. Increasing the fiber volume to 1.5% led to a further increase to cracking and ultimate loads by 41 and 48%, compared to those of the reference beam. Regardless of the failure mode, fibrous concrete beams eventually collapsed from the severely localized deformations at one or two major cracks.

2. It was found that fiber reinforcement can reduce the amount of shear stirrups required, and that a combination of web reinforcement and fibers resulted in obtaining the benefit of both high capacity and ductility. This combination resulted in a significant increase in the cracking and ultimate loads by 123 and 59% over those of the reference beam specimen. The hooked-end fibers are slightly better than corrugated steel fibers in terms of raising the first crack load, increasing the capacity and ductility of studied beams.
3. It was found that shear strength results for beams in the current investigation, subjected to axial compression stress equals 0.1, are 22-98% higher than those tested by Farahat<sup>16</sup> without applying axial stress. Increasing the applied axial compression stress from 0.1 to 0.2 led to a maximum increase in the first crack load and ultimate load by 24 and 10%, and a reduction of the deflection by (19-30%) and it has almost the same effect as increasing the fiber content from 0.5 to 1% on the ultimate shear capacity of the tested beams. The effect of increase in axial compression stress level becomes less significant with the increase of percentage volume of fibers from 0.5% to 1.5%.
4. A proposed equation was developed to predict shear strength of HSFRC beams with and without stirrups and subjected to axial compression stress. The results obtained using this equation were in good agreement with the experimental results of the tested beams. In addition, the results obtained by the proposed equation were in better agreement with the test results (mean of 1.0 and standard deviation of 0.08) when compared with the predictions based on the empirical equations proposed by other investigators.

Table 4 Comparison between the Proposed equation and Equations in Literature, modified to count for axial loading, in Predicting Shear Strength

Beam	Level of axial comp. stress	$f_{cu}$ , MPa	Observed shear strength, $v_{uo}$ , Mpa	Experimental / Predicted shear strength, $v_{uo}/v_p$			
				Narayanan & Darwish <sup>15</sup>	Ashour et al. <sup>2</sup>	Farahat <sup>16</sup>	Proposed Eq. (2)
B1	0.1	90	6.2 (3.33)	1.21	1.29	1.15	1.05
B2	0.1	91	6.7 (4.13)	1.15	1.15	1.04	1.01
B3	0.1	90	7.9	1.22	1.18	1.07	1.09
B4	0.2	84	6.8	1.02	1.1	0.98	0.90
B5	0.2	77	7.1	0.99	1.01	0.92	0.89
B6	0.2	76	8.1	1.02	1.0	0.92	0.93
B7	0.1	84	9.6 (7.85)	1.23	1.17	0.75	1.01
B8	0.1	79	5.1 (3.77)	1.0	1.28	0.98	0.91
B9	0.1	85	6.2	1.27	1.42	1.26	1.14
B10	0.1	86	6.5	1.17	1.27	1.14	1.08
B11	0.2	79	6.6	1.04	1.17	1.03	0.93
B12	0.2	80	6.7	0.94	1.02	0.91	0.86
B13	0.1	78	5.3 (2.67)	1.36	1.56	1.33	1.14
B14	0.1	78	6.6	1.15	1.26	1.13	1.05
B15	0.1	79	7.8 (4.13)	1.16	1.25	1.14	1.08
B16	0.1	78	7.9 (5.17)	0.97	1.04	0.96	0.94
B17	0.1	84	7.2	1.03	1.11	1.02	0.98
B18	0.1	80	8.3 (5.2)	1.08	1.15	1.07	1.05
B19	0.1	82	8.5 (6.0)	0.93	0.98	0.92	0.92
Mean				1.1	1.18	1.04	1.0
Standard Deviation				0.12	0.15	0.14	0.08

\* Values in parentheses are results of beams tested by Farahat<sup>18</sup>, not subjected to axial forces.



## ACKNOWLEDGEMENT

The staff members and technicians of the Reinforced Concrete Testing Laboratory at Cairo University are acknowledged for their great help.

## REFERENCES

1. Noghabai, K., "Beams of Fibrous Concrete in Shear and Bending: Experiment and Model" *Journal of Structural Engineering*, Vol. 126, No. 2, February, 2000, pp. 243-251.
2. Ashour, S.A., Hasanain, G.S., and Wafa, F.F., "Shear Behavior of High-Strength Fiber Reinforced Concrete Beams," *ACI Structural Journal*, Vol. 89, No. 2, 1992, pp. 176-184.
3. El-Niema, E.I., "Reinforced Concrete Beams with Steel Fibers under Shear," *ACI Structural Journal*, Vol. 88, No. 2, March-April, 1991, pp. 178-183.
4. Swamy, R.N., and Bahia, H.M., "Effectiveness of Steel Fibers as Shear Reinforcement," *Concrete International: Design and Construction*, Vol. 7, No. 3, Mar. 1985, pp. 35-40.
5. Craig, R. J., "Structural Applications of Reinforced Fibrous Concrete," *Concrete International: Design & Construction*, Vol. 6, No. 12, Dec. 1984, pp. 28-32.
6. ACI 544.4R-88, "Design Considerations for Steel Fiber Reinforced Concrete," State of the Art Report by ACI Committee 544, Reapproved 1999.
7. Johnson, M.K., and Ramirez, J.A., "Minimum Shear Reinforcement in Beams with Higher-Strength Concrete," *ACI Structural Journal*, Vol. 86, No. 4, July-Aug. 1989, pp. 376-382.
8. Ozcebe, G., Ersoy, U., and Tankut, T., "Evaluation of Minimum Shear Reinforcement Requirements for Higher-Strength Concrete," *ACI Structural Journal*, Vol. 96, No. 3, May-June 1999, pp. 361-368.
9. Yang, E.I., Yi, S.T., and Morita, S., "Effect of Axial Restraint on Flexural and Shear Behavior of High-Strength Concrete Members," *Magazine of Concrete Research*, Vol. 56, No. 2, March, 2004, pp. 63-72.
10. Megget, L. M. and Fenwick, R. C., "Seismic Behavior of a Reinforced Concrete Portal Frame Sustaining Gravity Loads," *Bulletin of the New Zealand National Society for Earthquake Engineering*, 1989, 22, No. 1, 39-49.
11. Abdoun, S. G. (1998) "Effect of Axial Compressive Stresses on Shear Strength of High Strength Concrete Beams with Web Reinforcement" *Cairo University*, Ph.D.
12. Balaguru, P.N. and Shah, S.P., "Fiber Reinforced Cement Composites," McGraw-Hill, Inc., 1992, p. 196.
13. Oh, B. H., Lim, D. H., Yoo, S. W. and Kim, E. S., "Shear Behavior and Shear Analysis of Reinforced Concrete Beams Containing Steel Fibers," *Magazine of Concrete Research*, Dec. 1998, Vol. 50, No. 4, pp. 283-291.
14. Shaaban, I. G., "Shear Behavior of High Strength Fiber Reinforced Concrete Beams Subjected to Axial Compression Forces," *Scientific Bulletin, Faculty of Engineering, Ain Shams University*, Vol. 39, No. 4, December, 2004.
15. Narayanan, R., and Darwish, I. Y. S., "Use of Steel Fibers as Shear Reinforcement," *ACI Structural Journal*, Vol. 84, No. 3, May-June 1987, pp. 216-227.
16. Farahat, A.M., "Effectiveness of Steel Fibers on the Shear Resistance of High-Strength Reinforced Concrete Beams," *Engng. Res. Journal, Helwan University*, Vol. 91, Feb. 2003, pp. 35-55.
17. ACI Committee 318, "Building Code Requirements for Structural Concrete (ACI 318-99) and Commentary (318R-99)," American Concrete Institute, Farmington Hills, Mich., 1999, 391 pp.
18. ECCS 203-2001, "Egyptian Code for Design and Construction of Concrete Structures", Cairo, Egypt, 2001.